

Improving Tearing Resistance of Leather - Part 2

Prevention and Treatment of Low Tearing Strength in the Tannery

by

Ricardo Tournier* and Fernando Lado

Abstract

An appropriate tear strength is one of the main properties that concern customers and it is also a significant source of claims. The authors make a review of the production process, focusing on each step that can either damage the natural strength of collagen fibers or improve them, and therefore, the leather.

The aim of this work, divided in Part 1 and 2, is to transfer field tannery experiences collected over 40 years of activity in different tanneries, to colleagues that are looking for world class leather production. Part 1 has been published in *JALCA*, 116(12), 2021.

6.0 Deliming

During the deliming operation, there is a lowering of the pH and extraction of adsorbed and combined $\text{Ca}(\text{OH})_2$. There are numerous deliming agents and systems that, properly conducted, do not compromise physical properties.

As a consequence of the pH changes, the hides suffer a significant degree of deswelling.

It should be considered that high temperatures, above 30°C , are harmful to fibers because of collagen hydrolysis at this stage.

7.0 Bating

The use of enzymes at this stage, breaking down non-structural proteins, loosening and removing scud, slackening the hides and improving the elasticity and smoothness of the grain, deserves attention.

Bating agents are mainly from several origins: pancreatic, bacterial, fungal. The active content of bates are blends of enzymes designed to give particular effects. Even though collagen is resistant to general proteolytic enzyme activity, damaged-collagen because of scratches or insect bites, fresh or unhealed, delay in soaking or curing or alkali-damage, can be attacked by general proteases and be degraded. That is why enzymatic processes must be carefully controlled, for prolonged action, overdoses, temperature increase and details as uniform distribution of enzymes in vessels.

Never keep bated hides in stock even if washed, remaining bates inside keep working.

In summary, bating should be a short time process, lots with extended standard timing, label them as RISKY.

Visual and manual evaluation of bated hides is very important since up till now there is not an objective method for industrial control.

It is worth mentioning that in comparative production trials in an upholstery tannery, increasing 10 times the % of normal bating enzymes keeping the bating time fixed, it was found that the average tearing strength increased by 10%. This could be explained because of the loosening of hides' structure that allowed better fiber movement and alignment to resist tearing forces.

8.0 Pickling

Although the pH lowering of bated hides with acids in presence of sodium chloride to prevent acid swelling seems very simple, it is a complex and dangerous step regarding physical properties in general and tear strength in particular.

We all have learned about the destructive effect that swelling can have on collagen, being the acid swelling the most dangerous one. Even if swelling is supposedly under control, acid hydrolysis takes place due to the increasing temperature resulting from the drum mechanical action.

Figure 10 illustrates the drastic effect that increasing temperature has on hide substance hydrolyzation, via Belavsky.²⁸

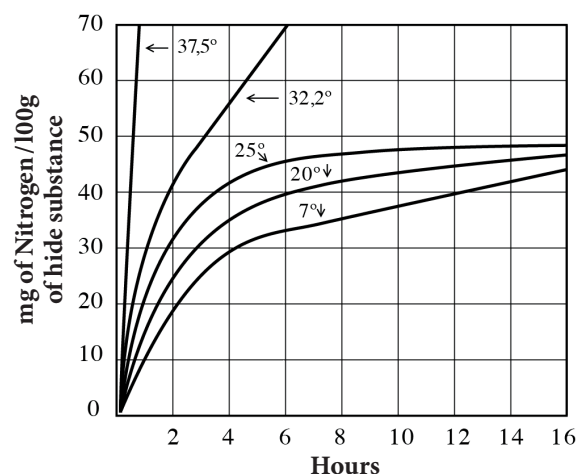


Figure 10. Pickle duration and temperature effect, on hide substance hydrolyzation²⁸

*Corresponding author e-mail: tournric@adinet.com.uy

Manuscript received August 8, 2021, accepted for publication August 26, 2021.

Given the complexity and dangers of the variables, the following factors must be taken into account to have this process under control and avoid irregularities as much as possible. Irregularities that otherwise will be reflected in tearing abnormalities.

- Pickle results will depend on the degree of delimiting, mainly in full substance hides.
- Float percent and drum rotation must be such that the increase of drumming temperature be as low as possible.
- Low rotation peg drums have the disadvantage of producing low mixing action, and if liquid products are added through the hollow axle, it will take them too long to arrive to the other side of the drum. In the meantime, part of the hides will be subjected to a higher concentration of products decreasing down to equilibrium, while another part will be subjected to a zero concentration up to equilibrium. The result is that the batch of skins will not be uniform. Better mixing action at low rotation speed can be obtained with drums with deep shelves.
- Cooling hides with ice cubes before starting pickle is a good practice. For instance, starting the process at 15°C and not going over 18°C at the end.
- Start with a small % of NaCl to drained hides and allow salt be taken up to prevent acid swelling. Complete the float with a mixture of brine that fits the requirements with sulfuric acid cooled down overnight, is also a good practice.
- To totally avoid the use of sulfuric acid in the pickle is a much better practice. Not only because the danger of personal or environmental accidents, but also because dosage mistakes can be the cause of physical properties irregularities very difficult to trace back and assign later on.

8.1 Tear strength loss estimate

Since the authors could not find in the literature a direct relation between tearing strength variation with pickle temperature, there is one presented here.

The following test was carried out in a tannery working with traditional pickle.

One lot of limed and split hides was divided in two and processed in two tanning drums.

One drum with normal pickle that ended normally with 28°C after 4 hr. running. In the other drum, hides were cooled down as well as the float water in such a way that after 4 hr. running the pickle ended at 23°C.

The rest of the tanning process was done in the standard way up to wet blue state.

Table II

	Means N/mm	STDEV
Normal 28 °C	29.8	8
Trial 23 °C	33.1	6.4

The hides were identified, shaved, mixed and followed standard process up to crust state where they were sampled for tear test IUP 8, 40 samples for each trial. Results are shown in Table II

The two means are significantly different with $P = 0.045$

It is interesting to observe that not only the strength at 23°C is higher but the standard deviation is lower.

Now these results can be associated with the data of Figure 10 to find a relation between tearing strength variation and pickle temperature.

Extrapolating values from Figure 10 for 4 hr running time and 18, 23, 28 and 32°C, the loss of hide substance at these temperatures can be estimated.

With these figures and tannery data of Table II, the behavior of leather tearing strength with pickle temperature is estimated as shown in Figure 11.

Taking 28°C as the basis of calculation, the tannery found that going from 28° to 23°C increased the tear strength from 29.8 to 33.1 that is 3.3 N/mm.

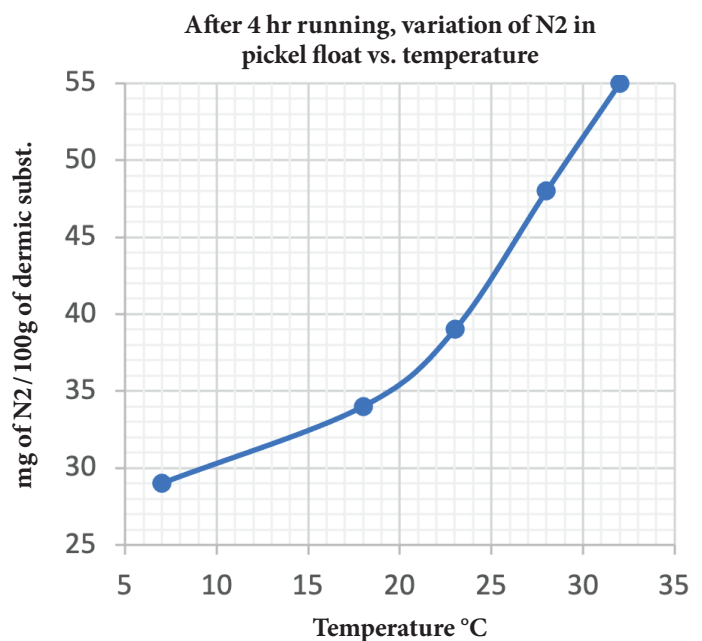


Figure 11. Variation of hide substance in pickle float vs. Temperature, with 4 hr running time

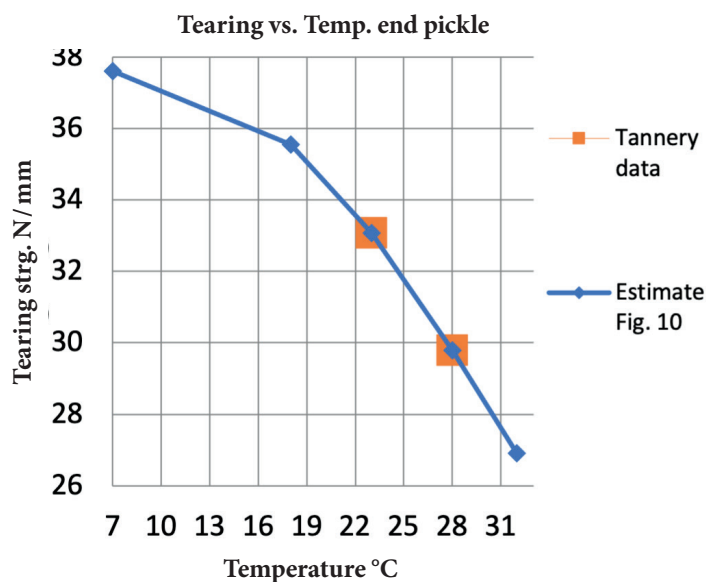


Figure 12. Tearing strength variation vs. end pickle temperature

From Figure 11, going from 28°C (48 mg of N₂) to 23°C (29 mg of N₂) 9 mg of N₂ were saved meaning that each unit of dermic substance equals 0.41 N/mm.

With these data the following graph is made.

Figure 12 shows the dramatic influence of temperature variations on tearing in traditional pickle.

Despite its strong influence, this factor was generally underestimated.

This illustrates that, in order not to damage the collagen fibers, work must be done with non-swelling acids and other auxiliaries or try new no-pickling chrome tanning systems.

Nowadays there are numerous proposals using different chemical products and systems to achieve this.

In any case, the suggestion is to test any of the commercial proposals on the tannery floor, with the sequential sampling method employed by Tournier,⁹ to confirm the collagen non-altering effect of the product or system used.

9.0 Chrome tanning

Although there are many references about the influence of chrome tanning itself on tear strength²⁰ not all of them are coincident whether it increases or decreases tear strength. There are divergences among different researchers and there is not a consensus.

Under our leather technologist experience, we adhere to the branch that states that chrome tannage itself decreases in some degree tearing resistance and can extend it to vegetable tanning.

Bienkiewicz, 1983,²¹ is very clear with the concept that with the introduction of tanning agents into the hide, some “dilution” effect of native collagen properties could be expected. Also, Lollar²⁹ states clearly that “...the tanned fiber is weaker than the untanned fiber.”

What else can be said about chrome tanning itself?

- That the chrome distribution must be as uniform as possible through the leather thickness
- The total chrome content, pH, differential pH, ash, humidity and grease content, must be within reasonable limits lot by lot
- Good mold development resistance
- Color uniformity and absence of stains

At least, all these parameters must be agreed upon between buyer and seller when commercializing wet blue.

It could happen that in the future, when buying and selling split or shaved wet blue, the wet tearing strength would be included as a requirement.

10.0 How to select stronger hides

In the Introduction it was said that tanneries apply heavy weight hides to produce low substances articles, compromising physical properties.

Later on, it was explained that collagen fibers in the corium layer of a hide or skin give leather its strength; the grain layer on its own is relatively weak. Consequently, if an excessive quantity of corium is removed by splitting and shaving, the leather will become weaker, as shown by Covington.¹ The grain to corium ratio should be lower than 50%.

Also, it is generally known that strong leathers show thinner grain layer than weak ones.

In Section 1.7 we cited Dr. Haines stating that physical properties are more a function of original hide thickness than breed or age of slaughter. A direct conclusion is: in order to produce thin leather, select thin hides.

The question is: How could all this information be translated to the tannery floor in a practical way?

In order to find a non-theoretical method to select stronger hides for demanding leather articles, the following assay was conducted in a tannery.

At the exit of a full substance wet blue hide sammying machine, equipped with a continuous substance measuring device, the hides were selected according to the thickness in the kidney area.

Hides were classified in following ranges:

Range I:	< 4 mm, number of whole hides 42
Range II:	4.1-5, 42
Range III:	5.1-6, 27
Range IV:	6.1-7, 23
Range V:	> 7 mm, 2 whole hides
Totaling	136 whole hides.

All hides were marked for range traceability, split to 1.7 mm, shaved to 1.3 mm, cut in sides and processed up to crust for shoe upper leather.

Finally, the 272 sides were sampled in the official area, parallel direction only, tested for continuous tear with ALCA method E 10 (trouser tear) and expressed results in Newtons.

The following graph, Figure 13, shows the results.

In this way we put numbers to Mrs. Haines and Covington statements and suggest a method to improve tearing strength in the tannery, selecting stronger hides.

For tanneries splitting in the lime, a continuous substance measuring device can be applied either at the exit of the lime fleshing or at the entrance of the splitting machine. Nowadays there are splitting machines in the market that measure thickness at the entrance of hides and automatic continuous programmed adjustments of splitting substance can be accomplished.

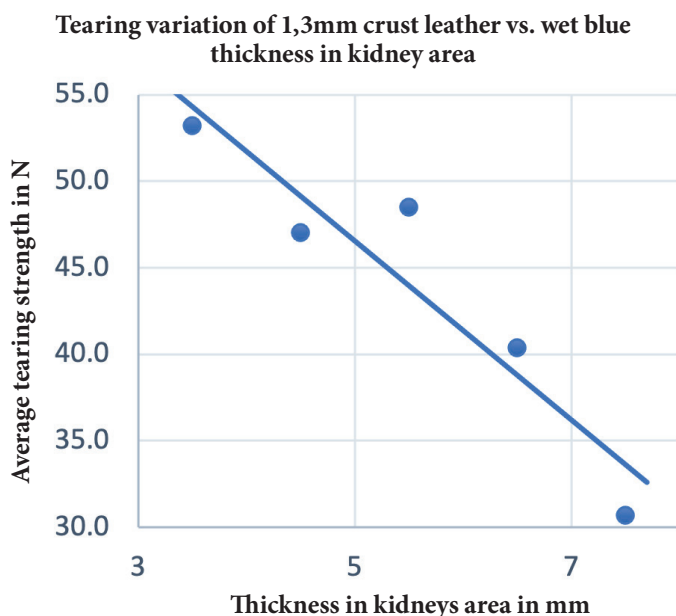


Figure 13. Relation between thickness in kidney area and tearing strength of crust leather.

11.0 Vessels and mechanical action

There are several vessel types: traditional drums, Y drums, paddles, mixers, washing machine types, etc.

If on top of these variety, different sizes, rotational speeds, internal additaments (pegs, shelves, etc.), loads, floats, times of processing, etc. are added, it happens that there are numerous variables and degrees of mechanical action.

The election and administration of these variables is handled discretionary by tannery technicians according to the equipment of each tannery, their expertise and results desired over leather.

Even though mechanical action promotes penetration, excessive mechanical action can produce not only grain abrasion but increase fiber disruption affecting tearing strength among other properties.

12.0 Post tanning operations

12.1 Neutralization

Mild and complete penetration of neutralization proved beneficial to tearing strength since it helps in the uniform distribution of subsequent products applied.

In particular, according to Altrock in 1995,²³ the use of sodium thiosulphate has been found beneficial for good tearing properties.

12.2 Retannage

Like the chrome tanning there are different opinions about if retannages increase, lower or not influence tear strength at all. Our position is to adhere again to the Bienkiewicz²¹ concept, that with the introduction of tanning agents into the hide, it is right to expect some “dilution” effect of native collagen properties. Hence, a tendency to lower physical properties, depending of course on the type and quantity of products can be foresee.

Another important point to consider is the overall effect of retannages and fillers. They can increase the substance of original shaved leather or not influence it at all.

Here again, it depends on the type and quantity of products.

As a rule of thumb, if the retannage and filler increases the substance of a particular crust and to maintain the customer agreed substance, it is necessary to lower 0.1 mm the shaving substance, the average tearing strength of the lot will be lowered in 10% approximately.

In this case the quantity of low tearing values will increase and the risk of customer claim also increases. Instead, it is worth trying to lower the retannages and filler load and not to modify shaving substance.

12.3 Fatliquoring

The fatliquors are the only products that certainly improve tearing strength and other physical properties. Their function is to lubricate fibers and fibrils impeding them to re-stick when leather dries out, allowing them to slide over one another, once leather is dry at equilibrium humidity.

This sliding makes for flexibility and softens the leather and help fibers to align in the sense of the strain in any direction, as explained in point 1.2.

In 1953 Benskin,²² studying several factors influencing tear and tensile strength found that tear strength increases rapidly from a zero-grease content to a maximum at about 10% grease, but subsequent increase does not add appreciably to the strength. He also found that a commercial upholstery leather with 11,5% grease, when degreased, the tear strength fell by over 31%.

Bitcover and Everett²³ in 1973, studying the separate influence of chrome and fat content on crust leather found an inverse correlation with chrome content and tear strength and a direct correlation between fat content and tear strength.

Personal experiences of the authors confirm this trend and can add the following comments:

After reaching the maximum tear, further increase of fatliquors tend to lower the strength.

In order to reach with fatliquors a complete penetration up to the finest components of the collagen structure, distribute them in multi-stage applications with smallest particle size emulsions.

Choose the appropriate fatliquors for each of these steps: pickle/tanning, neutralizing, retanning and main fatliquoring.

Play with the preparation of fatliquor emulsion, water in oil or oil in water, to find the method that gives the smallest particle size emulsions. And keep rutinary test tube samples of each main fatliquor emulsion prepared for each lot, to control the thickness of the cream formation, next day.

12.3.1 Mitigation of low tearing with oils

It can happen in any tannery that in a certain moment due to an alert from the control system or a customer complaint, we realize that the tear values are low. In the meantime, technicians start to investigate the possible cause, the problem can be mitigated for the leather in the pipeline by a modification of the main fatliquor, for instance.

Facing a real problem in a tannery and knowing that it is the neutral oil that is the real lubricant¹ we performed several pilot plant trials

adding different percentages of raw winterized neatsfoot oil to the mixture of oils of the main fatliquor, comparing against the normal formulation for shoe upper. We used 8 wet blue hides shaved 1.5 mm for a shoe upper crust. The hides were halved and the sides properly marked. The 16 left and rights sides were processed together up to the end of retannage. Afterwards, three lots were prepared. Lot 1, with 8 sides, 4 lefts and 4 rights, and the 8 sister sides were put in Lot 3. Lot 2, with 8 sides, 4 lefts and 4 rights, and the sister sides went to Lot 3 totaling 16 sides.

According to the WB average side shaved weight, the fatliquor formula weight was calculated for each lot.

Lot 3 (16 sds.) normal fatliquor as blank, Lot 1 (8 sds.) normal fatliquor plus 0,5% of winterized neatsfoot oil and Lot 2 (8 sds.) normal, plus 1,0%.

Following graph in Figure 14 shows the results of tearing strength in N/mm of final crust.

The improvement in tear was obvious, but the additional oil started to affect negatively the article characteristics. With 1%, the softness was excessive producing a coarse and sugary grain and looseness in pockets, veins were more evident and somewhat excessive elongation.

In this particular case, technicians chose 0.6% to overcome the problem.

12.3.2 Mitigation of low tearing with moisture

Humidity is another factor influencing tear strength. Each leather article has different equilibrium moisture according to the ambient

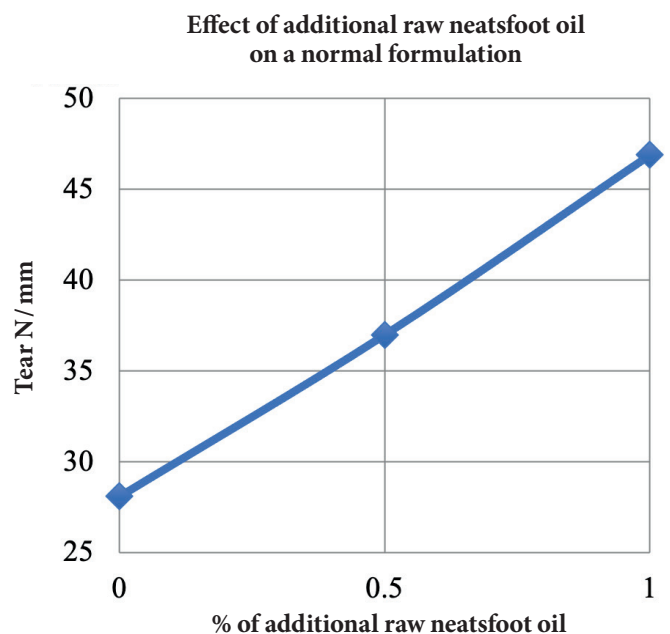


Figure 14. Effect of neatsfoot oil in tearing strength.

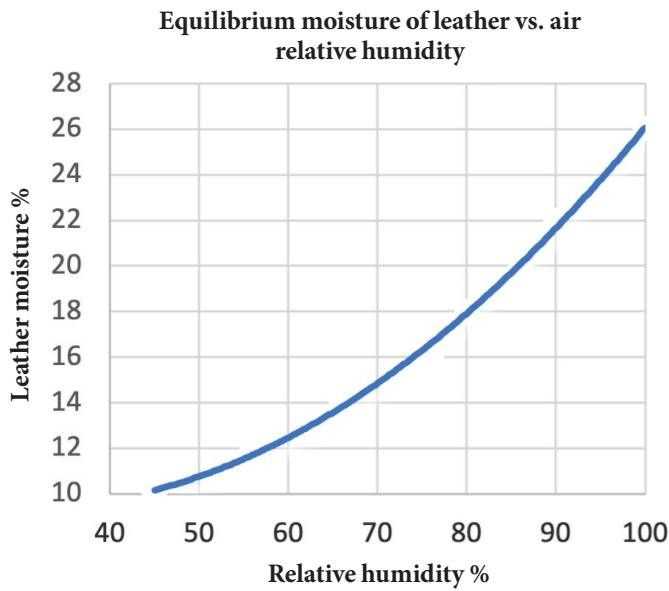


Figure 15. Equilibrium leather moisture vs. ambient humidity.

humidity where it is placed. In the following graph, Figure 15, is represented the general tendency to absorb humidity of finished leathers.

In order to see the influence of different leather moistures content in tear strength, we performed the following study.

We extracted official samples out of 50 sides of a shoe upper crust, 1.6/1.8 mm. Samples were cut for double edged (slit) tear resistance, IUP 8, perpendicular to backbone, 3 cuttings for each sample. So, there were 3 sets of 50 cuttings per set.

Each set was stored 48 hr in a hermetic chamber with different relative humidity at 25°C, namely: (1) water, (2) salts in water and (3) concentrated sulfuric acid. After each one of the 48 hr, leather moisture was measured with 2 methods, AquaBoy readings and drying to constant weight in an oven at 102 ±2°C, Table III

Finally, tear resistance was measured according to double edged slit method, IUP 8.

Table III

	Group		
	1	2	3
Humidity	Low	Medium	High
AquaBoy	6/8%	12/14%	22/24%
Oven	11%	16.5%	26%

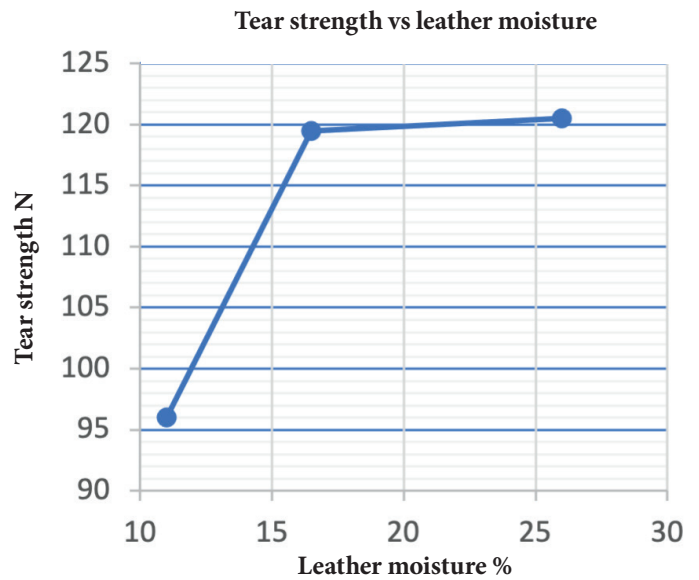


Figure 16. Evolution of tear resistance with leather moisture.

Results are in the following graph of Figure 16

This means that:

- Leathers coming out of the tannery with low humidity should be avoided. Otherwise, moisturize finished leather. Not only to preserve physical properties, but also softness, area, substance, etc.
- Avoid leathers with more than 16% moisture because of danger of mold development in stock.
- Fatliquoring agents containing lanolin and other auxiliaries can regulate moisture content.
- Quite often, leathers coming out of the finishing room after suffering tunnel dryers, show moistures well below 10%. These leathers will have tear resistance 15% lower than the same with normal moisture. This strength loss can be recovered easily by moisturizing them.
- Inversely, leathers with border line strength at normal moisture, by means of moisturizing, can increase about 10% resistance.
- In some cases, it is possible to add an appropriate fatliquor to the moisturizing solution, to boost and lengthen the effect.

12.4 Drying and softening

This is another processing step that, if not well designed, standardized and controlled will affect leather quality, area yield, physical properties and hence, tearing resistance.

In this step, experience and expertise of tannery technicians are of utmost importance.

The evolution of the temperature gradient and the time in each dryer depend on too many factors to arrive to the desired article. Ideally the target is to obtain the desired moisture inside the leather at the end of the dryers that after a certain period of stocking time, for unifying the moisture, the lot reaches an adequate and uniform moisture to be subject to softening.

In general, it can be said that the softening moisture should be 18/24%. Lower than this can produce breaking of fibers during softening. Higher than 24% will force to dry again, to avoid the leather going to the next step developing mold and/or risking new stiffness.

Some comments and suggestions:

- The sammying operation previous to drying is justified since it is cheaper to eliminate water by pressing than by heating, but the lowest possible water content to be attained is about 55%, if higher pressure were to be applied the fiber structure starts to be destroyed, Heidemann.²⁴
- Overheating in the dryers must be avoided since it can cause sticking of the fibers and even modify the inner structure of the fibrils. Both factors affect tear strength.
- Control differential pH of running production. Values higher than 0.7 indicate presence of strong acids, generally sulfuric. During drying, water evaporation produces the increase of concentration of acids present between fibers and fibrils with the corresponding increase of hydrolysis of collagen and destruction of them.
- Tension and toggle dryers must be dully controlled since drying normally produces shrinkage of leather adding extra tension that can break fibers and even tear the leather around toggles.

12.4.1 Vacuum drying

Even though there are several guidelines to work with each different type of dryers and their combinations, leather technicians use their experience, tradition and trial and error to adjust the drying and softening process for each article.

Regarding vacuum drying it is interesting to mention the work of Liu and DiMaio, 2001²⁵ about the correlation they found between the drying rate and tearing strength.

They defined the drying rate Ω as:

$$\Omega = (W_o - W_t)/(t)^{1/2}$$

where, W_o is the initial water content and W_t , residual water content at time t .

The relationship between tear strength and drying rate

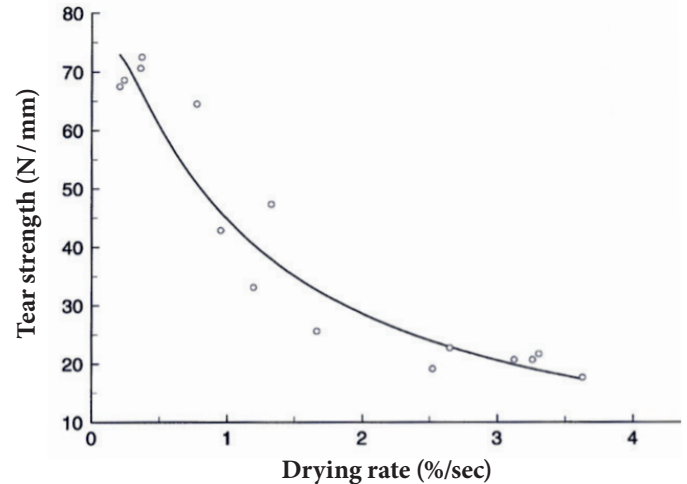


Figure 17. Tear strength vs. drying rate (With JALCA permission)

Figure 17, (Figure 5 in the original paper) demonstrated that tear strength correlates inversely with the drying rate.

According to the authors, their study has shown this newly defined drying rate dictates the resultant tear strength.

12.4.2 Softening

Staking and milling are the main mechanical operations to liberate fibers from adhesions between them during drying, that stiffen leather.

There is a direct interaction between fatliquoring, moisture, degree of softening and tear strength. This is another area where, to determine the perfect equilibrium among these and other factors for each article, requires a great amount of experience in the art of leather making.

Increasing softness increases the ability of fibers to align in the sense of the applied force, then, increases tear resistance.

But too much mechanical action starts to break fibers and lowers tear resistance.

Edmonds et al.²⁶ determined that, between unmilled and milled leather, there are average increases of about 4% in tear strength expressed as N and N/mm, about 8% in thickness and about 50% in softness (BLC Softymer).

12.6 Finishing

Although the finishing operations affect mainly the surface of leather, there are some steps that have important influence in the physical properties and in particular, tear strength.

The application of different types of coats with different type of machines, imply the humidification of leather with subsequent dehumidification through drying tunnels.

The tunnels are designed to dry as fast as possible and generally over dry leather.

The ideal finishing tunnel, in our concept, is the infrared heated, but even in this case, the over drying exists in practice.

This over drying produces hardening of leather that must be corrected by additional softening, risking lowering tear resistance.

This hardening effect is critical when it comes to impregnations.

Additional heating and hardening is produced with embossing and plating.

The general picture at the end of the finishing lines is that leathers come out with very low moisture, well below 10-14% that should be the normal.

Sending this leather to customer, the tannery is risking several dangers, namely:

- Losing about 3% area yield, Figure 18 illustrates it.
- Claim if customer click templates, the component pieces are stacked in a humid environment, they absorb humidity, and change shape and size.
- Low tear strength according to discussed in 12.3.2 and Figure 16.

To correct this situation, leathers must be humected with water and some auxiliaries, by means of roller coating machines or spraying machines taking care of not to damage the grain side, or by hanging in humidifying rooms or tunnels set to 65-70% of relative humidity, see Figure 15.

The ideal situation would be to maintain the equilibrium moisture of the leather along the finishing room.

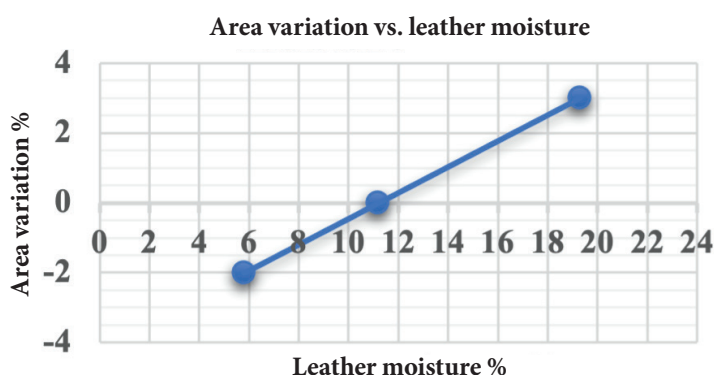


Figure 18. Area yield vs. leather moisture



Figure 19. Digital Scale with Hook

13.0 Final sampling

Generally, all lots ready for shipment are tested to check that they are up to standard for each customer.

In this sense, the work of Azzato and Tournier, 2019,²⁷ regarding the selection of a sampling plan to have sufficient protection not to send problems to customers, produces results of interest. They evaluate the different possibilities taking as working example the tear resistance of ten lots of the same article, of approximately 100 pieces each. The lots were 100% sampled in the official sampling area and tested with IUP 8 standard method.

13.1 Tearing, field manual testing

There are situations when it is necessary to check lots 100% to segregate substandard pieces with low tear strength.

This work is possible to perform by means of one of the numerous manually digital scales in the market, as the one in Figure 19.

A possible procedure is to make one or two incisions of 4 or 5 cm in the area of the official sampling, parallel to backbone, place the hook of meter and pull in the same way it does the lab dynamometer performing IUP 8 method.

It resembles the standard method by tearing a double edge slit.

In this way it is possible to segregate weak pieces that later can be checked out with the standard method in the laboratory.

14.0 Artificial improvement of tearing

From long ago, there have been attempts to increase leather strength, tearing in particular, by means of deposition of different polymers within the leather structure.

Vinyllic, acrylic, polyurethane and other compounds are being studied.

Although there have been some successful applications, the leather treated in this way changes to a great extent the desired characteristics of normal leather.

Therefore, preservation and care of native collagen properties is the utmost objective of this paper and should be the same for leather technicians.

Conclusions

As seen along this paper there are many steps to take care of collagen fibers, that confer the strength to leather.

Among them, one of the most important ones are the steps between the flaying and the soaking that starts the leather processing.

The utmost care taken, protecting the original collagen fibers from degradation, not only will give good physical and subjective properties but high standard production level and yield. Also, the constant monitoring of different variables and quality, and the fine tuning of them, contribute to the final success of customer satisfaction.

It is our hope that some of the topics covered in this paper will serve as motivation and inspiration to the scientific leather community to deeply study them with the scientific rigor they deserve.

Acknowledgements

The authors would like to thank Germán Azzato, Jaime Velez and Juan Carlos Oclepo from SADESA Group International and Maria Rubino Professor at Michigan State University, E. Lansing, MI, for corrections and constructive criticism of the text.

References

20. Tournier, R.; Tanning Chemicals' Influence in Leather Tensile and Tear Strength Review, *JALCA*, **115**, 11, 2020
21. Bienkiewicz, K.J.; Physical Chemistry of Leather Making, Krieger Pub. Co., Malabar, Florida, USA, (1983), 314.
22. Benskin, G.E.; Some Factors Influencing the Tear and Tensile Strength of Split Hide Leather, *JSLTC*, **37**, 126-142, 1953.
23. Altrock, H.; Factors influencing the tear resistance of leathers, *World Leather*, 51, May 1995.
24. Heidemann, E.; Fundamentals of Leather Manufacturing, Eduard Roether KG, Darmstadt, 542, 1993.
25. Liu, C.- K., and DiMaio, G.L.; Effects of Vacuum Drying Variables on the Mechanical Properties of Leather, *JALCA* **96**, 243, 2001.
26. Edmonds, R.L, Peruzzi, A. and Cooper, S.; The Impact of Milling on Leather Properties and Fatliquor Distribution, *JSLTC*, **101**, 312, Sept. 2017.
27. Azzato, G., and Tournier, R.; Sampling plans for evaluation of leather physical properties, *World Leather*, 21, April/May 2019.
28. Belavsky, E.; Curtume no Brasil, Livraria do Globo, P.A., Brasil, 215, 1965.
29. O'Flaherty F., Roddy, W.T. and Lollar, R.M.; The Chemistry and Technology of Leather, Vol. 2, 10, Krieger Pub. Co., New York, 1978.